

Field induced $d_{x^2-y^2} + id_{xy}$ state and marginal stability of high- T_c superconductors

A.V. Balatsky

T-Div and MST-Div, Los Alamos National Laboratory, Los Alamos, NM 87545, USA

(February 1, 2008)

It is shown that the *complex* d_{xy} component is generated in d-wave superconductor in the magnetic field. As one enters superconducting state at finite field the normal to superconducting transition occurs into bulk $d_{x^2-y^2} + id_{xy}$ state. The driving force for the transition is the linear coupling between magnetic field and non zero magnetization of the $d_{x^2-y^2} + id_{xy}$ condensate. The external magnetic field violates parity and time reversal symmetries and the nodal quasiparticle states respond by generating the id_{xy} component of the order parameter, with the magnitude estimated to be on the order of few Kelvin. Parity (P) and time reversal (T) symmetries are violated in this state.


PACS numbers: 74.20.-z, 74.25.Dw

Symmetry of the order parameter and existence of the gap nodes in high- T_c superconductors has been one of the main experimental questions addressed for the last few years. By now the majority of the data support the d-wave symmetry of the order parameter [1–4]. However, recent experiments on thermal transport in BiSrCuO superconductor reveal a number of anomalies, prompting the suggestions that the secondary superconducting order parameter is developed in the external magnetic field, thus lowering the symmetry of the initial $d_{x^2-y^2}$ to order parameter that contains more than one distinct components [5,6].

Based on the data it was suggested that first order phase transition from original $d_{x^2-y^2}$ -wave (d) to $d_{x^2-y^2} + id_{xy}$ ($d + id'$) state occurs abruptly in the magnetic field. Theoretical approach, describing this transition as an abrupt bulk generation of the secondary id' component upon increased field was proposed [7–9]. It was also found that the vortices play an important role in the observed anomaly [6,10].

Motivated by these experiments I present here the alternative approach to the field induced $d + id'$ transition in high- T_c superconductors. I focus on the high field region $H \simeq H_{c2}$ where vortices are so dense that they eventually destroy superconducting state. In this regime I still find that the d-wave state can be “distorted” by the external field, producing $d + id'$ state in the bulk with the intrinsic orbital moment, Figs.(1,2).

D-wave superconductor has low energy quasiparticles in the nodes of the d-wave gap. These low lying states have a vanishingly small gap and hence can easily respond to the external perturbations [11]. This fact opens up the possibility to generate the second component of the order parameter, orthogonal to the initial d-wave state, from these “normal” quasiparticles at the nodes. This softness of the d-wave state to the secondary component generation in the presence of perturbations, such as scattering on the surface [12,13] or the magnetic impurity scattering [14,15] is the reflection of the *marginal* stability of d-wave superconductors [16].

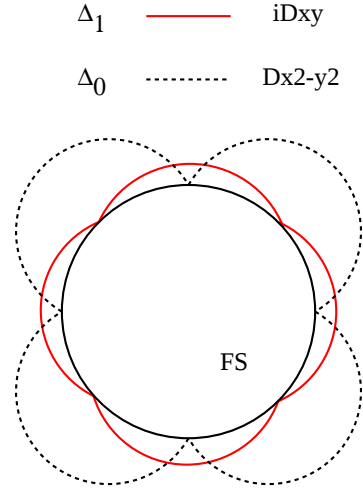

$$\text{FULL GAP} = (\Delta_1^2 + \Delta_0^2)^{1/2}$$

FIG. 1. Fermi surface (FS), taken to be cylindrical, is shown with the angular dependent $\Delta_0(\Theta)$, $\Delta_1(\Theta)$ gaps. The $d + id'$ state is fully gapped because for the complex order parameter the particle gap will depend on sum of squares of real (d) and imaginary (d') amplitudes.

Here I consider the case of external magnetic field and argue that the normal to superconducting transition in the field occurs into bulk $d + id'$ state: d-wave state is *marginally stable* in the field. Magnetic field $H||z$ violates P and T symmetries. The superconducting state responds to the field by generating the id_{xy} component so that the total order parameter symmetry in the bulk becomes $d + id'$.

The physical origin of the instability is the bulk magnetic moment $\langle M_z \rangle$ in $d + id'$ state. First I present a qualitative argument for id' induction by the external field. The relevant interaction is the $\langle M_z \rangle B$ coupling to the magnetic field $B||z$, where B is the induction in external field H . In the pure phase one can think of d-wave state as an equal admixture of the orbital moment $L_z = \pm 2$ pairs:

$$\Delta_0(\Theta) = \Delta_0 \cos 2\Theta = \frac{\Delta_0}{2}(\exp(2i\Theta) + \exp(-2i\Theta)) \quad (1)$$

Here Θ is the 2D planar angle of the momentum on the Fermi surface, Δ_0 is the magnitude of the $d_{x^2-y^2}$ component. Motivated by the layered structure of the cuprates, I consider 2D $d_{x^2-y^2}$ superconductor. In the presence of the external field H the coefficients of the $L_z = \pm 2$ components will shift *linearly* in B with *opposite* signs:

$$\begin{aligned} \Delta_0(\Theta) &\rightarrow \frac{\Delta_0}{2}((1 + \eta B) \exp(2i\Theta) \\ &+ (1 - \eta B) \exp(-2i\Theta)) = \Delta_0(\Theta) + i B \Delta_1(\Theta) \end{aligned} \quad (2)$$

where $\Delta_1(\Theta) \propto \eta \sin 2\Theta$ – is the d_{xy} component and η is the coupling constant. The relative phase $\pi/2$ of these two order parameters comes out naturally because $d + id'$ state has a partially noncompensated orbital momentum $L_z = +2$. The pure d-wave state has nodes of the gap and generated id_{xy} gap will “seal” the nodes making the state fully gapped, as is shown in Fig.1.

To show how complex id_{xy} component appears, consider a macroscopic Ginzburg-Landau (GL) functional which allows the linear coupling between the original $d_{x^2-y^2}$ order parameter $\Delta_0(\Theta) = \Delta_0 \cos 2\Theta$ and the field induced d_{xy} component: $\Delta_1(\Theta) = \Delta_1 \sin 2\Theta$. The GL functional contains the *linear* coupling term:

$$F_{int} = i \frac{\eta}{2} \Delta_0 \Delta_1^* B + h.c. \quad (3)$$

where η is the macroscopic coupling constant, Eq.(2). This coupling is possible only for $d + id'$ and not for $d + is$ symmetry of the order parameter. The question I address here is to find the conditions when the second component is generated in the presence of the external field. I find that: a) instability into $\Delta_0 + i\Delta_1$ state occurs at $T_c(H)$ greater than the transition temperature for the initial transition $T_c^0(H)$ in the absence of the coupling F_{int} . Upon entering the superconducting state the symmetry of the condensate in the bulk is $d + id'$ from the outset, as is indicated in Fig.2. This is the main result of this paper. b) id_{xy} induced component is linear in the applied field $\Delta_1/\Delta_0 \propto H$.

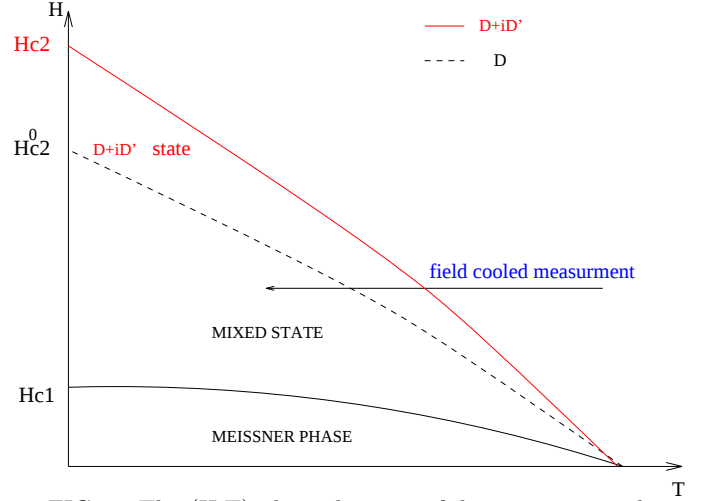


FIG. 2. The (H,T) phase diagram of d-wave superconductor is shown. The dashed line corresponds to the normal $\rightarrow$ superconductor transition in the absence of the $\Delta_0\Delta_1$ coupling: $H_{c2}^0(T)$. The solid line is the new phase boundary $H_{c2}(T)$ in the presence of the $\Delta_0\Delta_1^*$ coupling in the free energy. The $d + id'$ state has higher transition temperature and hence the first state to form below H_{c2} line is the $d + id'$ state in the bulk. The effect of the induced $d + id'$ state can be seen in the field cooled experiment, as indicated. The slope of the $H_{c2}(T)$ is linear at small T since the shift $\delta T_c(H)$, Eq.(7) is quadratic in H . I ignore here the effects of possible vortex melted phases. The new $H_{c2}(T)$ is drawn out of scale and is closer to the $H_{c2}^0(T)$ line. In this theory the $H = 0$ transition occurs into a pure d-wave state.

I start with the GL free energy of the d-wave superconductor in the vicinity of $H_{c2}(T)$ field. The input fields are: Δ_0 - $d_{x^2-y^2}$ -wave order parameter, Δ_1 - d_{xy} component and external field along z -axis H . I will consider the infinite two dimensional case, where all the gradients are in the (xy) plane only. Here for simplicity I also consider the case of $d_{x^2-y^2} + id_{xy}$ admixture only, ignoring any other components of the order parameter, that can be mixed in [17]. The reason is that $d_{x^2-y^2} + id_{xy}$ is the only singlet state on the square lattice where both P and T are broken and the condensate has nonzero orbital momentum $\langle L_z \rangle \sim i\Delta_0\Delta_1^* + h.c.$ [18].

The GL functional density takes the form:

$$\begin{aligned} F = \int dr [&\frac{\alpha_0}{2}(T - T_c^0)|\Delta_0(r)|^2 + \frac{\beta_0}{4}|\Delta_0(r)|^4 + \\ &K_{ij} |(D_i \Delta_0(r))(D_j \Delta_0(r)^*)|^2 + \frac{B^2}{8\pi} + F_{int} + \frac{\alpha_1}{2}|\Delta_1(r)|^2] \end{aligned} \quad (4)$$

where the first three terms describe the instability of the pure $d_{x^2-y^2}$ - wave superconductor, with T_c^0 being the critical temperature in the absence of the field. Tensor K_{ij} is the gradient tensor, which I do not need specify right now [19]. I used $D_j = \nabla_j - i \frac{e}{c} A_j$, $j = x, y$ in gradient energy, A_i - is the gauge potential. The last term describes the *positive* energy shift for the $d_{x^2-y^2}$ state in the presence of the induced secondary component d_{xy} .

The gradient terms for the induced d_{xy} component are ignored since I consider the case where Δ_1 is small and the gradient terms will lead to the small corrections [20]. F_{int} in Eq.(3) is discussed in more details below. For general discussion of the GL terms see [21,22].

From GL functional Eq.(4) it follows that the coupling to the external field, as far as the secondary id' component is considered, is linear in F_{int} . Whereas the stiffness term (last term in Eq.(4)) is quadratic. Therefore the linear term dominates at small $\Delta_1(r)$ and yields nonzero equilibrium value for $\Delta_1(r)$.

One can easily see that the only second order gradient term that couples Δ_0 and Δ_1 is :

$$D_x \Delta_0 D_y \Delta_1^* - D_y \Delta_0 D_x \Delta_1^* + h.c. \quad (5)$$

leading to, among other terms, $-i\frac{e}{c}B\Delta_0\Delta_1^* + h.c.$, where commutator $[D_x, D_y] = i\frac{e}{c}B$. Since there is no other terms that couple Δ_0 and Δ_1 in the gradient terms, I can write the coupling term without derivatives as is done in Eq.(3).

To show that the terms in Eqs.(5, 3) are indeed full invariants, recall that the square lattice group D_4 has irreps: A_1 (s-wave), $A_2 \sim z$, $B_{1g} \sim x^2 - y^2$ - $d_{x^2-y^2}$ -wave representation, $B_{2g} \sim xy$ - d_{xy} representation, all of them one dimensional and one two-dimensional representation: $E \sim (x, y)$ - p wave [23]. Consider for example B_{1g} and B_{2g} coupling in Eq.(5): the the product of $\Delta_0\Delta_1^* \sim A_{2g}$. The direct product of two derivatives, transforming as E each, is a sum of all four one dimensional representations: $E \times E = A_{1g} + A_{2g} + B_{1g} + B_{2g}$. The antisymmetric combination $D_x D_y - D_y D_x = i\frac{e}{c}H \sim A_{2g}$ and I find that true scalar can be formed by taking the product of two A_{2g} representations $\Delta_0\Delta_1^*$ and $[D_x, D_y]$. Hence the interaction term Eq.(5) is a scalar and allowed in free energy. Eq(3) follows immediately. Alternatively, as indicated above, one can see that the $\Delta_0 + i\Delta_1$ state has a nonzero angular momentum state with expectation value of the magnetic moment of the condensate $\langle M_z \rangle \sim i\Delta_0\Delta_1^* + h.c.$. Therefore there is a linear coupling between external field and magnetic moment $F_{int} \propto -\langle M_z \rangle B$, Eq.(3).

Next, I use the fact that for $H \simeq H_{c2}$ the local field $h(r)$ is homogeneous and d-wave order parameter takes the form $\Delta_0(r) = \Delta_0 f(r)$, where $f(r)$ is a function of the position of the nodes of the order parameter, e.g. $f(r) = \prod_i (z - z_i) \exp(-|z_i|^2/4\ell_H^2)$ where $z_i = x_i + iy_i$ are the nodes of the order parameter for the case of pure d-wave with isotropic gradient term $K_{ij} = K\delta_{ij}$ and $\ell_H = (c/2eH)^{\frac{1}{2}}$ [24]. I will not specify the form of $f(r)$ which should come out as a solution for particular choice of the lattice of the nodes of the d-wave order parameter in our case. Instead I note that the Δ_1 field enters quadratically into GL functional and one can integrate over Δ_1 field, to obtain the effective theory for Δ_0 .

Treating Δ_1 and Δ_1^* as independent variables the minimization of the Gibbs energy $G = F - \frac{BH}{4\pi}$, $\partial_{\Delta_1^*} G =$

$\partial_{\Delta_1^*} G = 0$ leads to:

$$\Delta_1(r) = \frac{\eta}{i\alpha_1} H \Delta_0(r) + O(|\Delta_0(r)|^2) \quad (6)$$

hereafter I ignore small difference $B - H = -4\pi M_z \propto O(|\Delta_0(r)|^2)$ near H_{c2} , where Δ_0 is small. After substituting this result in Eq.(4) the free energy for Δ_0 acquires negative contribution $\delta F = -\int dr [\eta^2/2\alpha_1 H^2 |\Delta_0(r)|^2]$. I obtain the GL functional Eq.(4) with renormalized T_c^0 , which is now field dependent:

$$T_c^0(H) = T_c^0 + \delta T_c(H), \quad \delta T_c(H) = \frac{\eta^2}{\alpha_0 \alpha_1} H^2 \quad (7)$$

The standard next step is to solve the GL equations for the $\Delta_0(r)$, using the ansatz $\Delta_0(r) = \Delta_0 f(r)$ as discussed above [21,22,24]. One would find the free energy for the amplitude of the order parameter Δ_0 (now Δ_0, Δ_1 are *homogeneous fields* corresponding to the amplitudes of $d + id'$ order) with the field dependent $T_c(H)$:

$$F = \alpha(T, H)/2 |\Delta_0|^2 + \beta(T, H)/4 |\Delta_0|^4, \quad \Delta_1 = \frac{\eta}{i\alpha_1} H \Delta_0 \quad (8)$$

with $\alpha(T, H) = \alpha_0(T - T_c(H) - \delta T_c(H))$. The $\alpha(H, T)$ and $\beta(H, T)$ parameters will be determined by the vortex lattice structure. Here the vortex lattice is not specified explicitly and I assume that for given configuration one finds the solution. I write the general expression for thus determined $\alpha(H, T) \propto T - T_c(H)$ in the absence of the $\Delta_0\Delta_1^*$ coupling. It follows from Eq.(8) that this coupling will shift amplitude instability to higher fields/temperatures $T_c(H) \rightarrow T_c(H) + \delta T_c(H)$ as is shown in Fig.(2).

To estimate the amplitude of the induced Δ_1 one can use the BCS theory for the coefficients in the GL energy Eq.(4,8). These estimates are useful as the order of magnitude estimates at best. The coefficient η in F_{int} (in units of energy) describes the $\langle M \rangle H$ interaction with the orbital moment of the condensate and I estimate $\eta = \mu_B N_0^2$, where $\mu_B = \frac{e\hbar}{2mc}$ is the Bohr magneton, $N_0 = 1/eV$ per unit cell- is the density of states at the Fermi surface. α_1 was shown to be $\alpha_1 \simeq N_0/2$ [15]. Using $H_{c2} \simeq \phi_0/2\pi\xi^2$, with $\xi = 20\text{\AA}$ as the low temperature coherence length of superconductor, one gets $\eta \simeq N_0(H/H_{c2})(a/\xi)^2$, where $a = 3.8\text{\AA}$ is the atomic length in the Cu-O plane. From these estimates and Eq.(8) it follows that:

$$|\frac{\Delta_1}{\Delta_0}| \simeq (H/H_{c2})(a/\xi)^2 \simeq 10^{-2} \quad (9)$$

This makes the amplitude of the induced component $|\Delta_1|$ to be on the order of few K° . From Eq.(7) the shift of T_c turns out to be much smaller: $\delta T_c/T_c^0 \sim (H/H_{c2})(a/\xi)^4 \sim 10^{-3}$.

Eqs.(6,7) prove the points that a) the transition into $d + id'$ state indeed occurs at higher T_c if the $\Delta_0\Delta_1^*$ coupling is present and b) the field induced Δ_1/Δ_0 xy component is linearly proportional to the field. Whether the

existence of the induced id' component can be observed in experiments, such as penetration depth $\lambda(H, T)$, is an interesting question which is currently under investigation. It is possible that the secondary component will cause changes in the vortex lattice symmetry at low temperatures.

It is useful to note the relation of these results to the previous work. Laughlin argued for the coupling term similar to F_{int} , Eq(3), although the focus of his work was on the different part of the phase diagram $H_{c1} \ll H \ll H_{c2}$ [7]. It was predicted that the transition into $d + id'$ state to be of the *first* kind with the induced component $\Delta_1 \propto H^{\frac{1}{2}}$. In another approach, Ramakrishnan recently suggested the alternative mechanism to generate the $d + id'$ state in the bulk [8]. His approach is based on the finite id' component generated near the vortex cores. As one increases the vortex density the overlapped id' patches eventually produce the bulk id' order. The starting point there was the single vortex solution which is inapplicable at $H \simeq H_{c2}$. The relation between phases discussed in [7,8] and present work is unclear at a moment. One possibility is that there is a crossover or phase transition that separates high field $d + id'$ state, discussed here, from possible $d + id'$ state at lower $H \ll H_{c2}$ fields.

In conclusion, I argue that the normal-to-superconducting transition of the d-wave superconductor occurs into $d + id'$ state with the field induced secondary component id' with $\Delta_1/\Delta_0 \propto H$. Even if the interactions are repulsive in the xy channel this field induced component is present at finite fields $H \simeq H_{c2}$. The driving force for the id' induction is the linear coupling between orbital moment of the $d + id'$ condensate with the external magnetic field. Penetration depth λ and vortex lattice structure could be sensitive to the presence of id' gap and might be used to detect it.

I am grateful to D.H. Lee, V.P. Mineev and M. Zhitomirsky for the useful discussions. This work was supported by the US DOE.

[1] D. A. Wollman *et al.*, Phys. Rev. Lett. **71**, 2134 (1993).
[2] W. N. Hardy *et al.*, Phys. Rev. Lett. **70**, 3999 (1993).
[3] Z. X. Shen *et al.*, Phys. Rev. Lett. **70**, 1553 (1993).
[4] C.C. Tsuei and J.R. Kirtley, Proceedings of Spectroscopies in Novel Superconductors, 1997; Journ of Phys. Chem of Solids, **59**, 2045, (1998) and referencies therein.
[5] K. Krishana, *et al.*, Science, **277**, 83, (1997).
[6] H. Aubin, *et al.*, Phys. Rev. Lett., **82**, 624, (1999).
[7] R.B. Laughlin, Phys. Rev. Lett., **80**, 5188, (1998).
[8] T.V. Ramakrishnan, Journ. Phys. Chem of Solids, **59**, 1750, (1998) in Proceedings of Spectroscopies in Novel Superconductors 1997.

[9] M. Franz and Z. Tesanovich, preprint, cond-mat/9812126.
[10] Y. Ando *et al.*, preprint, cond-mat/9812265.
[11] In s-wave superconducting state, on the contrary, quasi-particles cannot easily generate the second component of the order parameter: finite gap on the Fermi surface requires the large perturbation to overcome the finite threshold, set by the gap.
[12] M. Covington, *et al.*, Phys. Rev. Lett., **79**, 277, (1997).
[13] M. Fogelstrom *et al.*, Phys. Rev. Lett., **79**, 281, (1997).
[14] R. Movshovich, *et al.*, Phys. Rev. Lett., **80**, 1968, (1998). and in Proceedings of Spectroscopies in Novel Superconductors, 1997; Journ of Phys. Chem of Solids, **59**, 2100, (1998).
[15] A.V. Balatsky, Phys. Rev. Lett., **80**, 1972, (1998), and in Proceedings of Spectroscopies in Novel Superconductors, 1997; Journ of Phys. Chem of Solids, **59**, 1689, (1998).
[16] A.V. Balatsky and R. Movshovich, Proceedings of SCES, Paris, 1998, Physica B, to be publ. cond-mat/9805345.
[17] V.P. Mineev, private communication.
[18] Here I ignore Zeeman splitting effects that are more important for the in-plane field configuration, e.g. K. Yang and S. Sondhi, Phys. Rev. **B 57**, 8566, (1998).
[19] There is a large body of literature on possible terms in K_{ij} , see for example: R.Heeb, A. van Oterlo, M. Sigrist and G. Blatter, Phys. Rev **B 54**, 9385, (1996) and in M. Palumbo, P. Muzikar and J. Sauls, Phys. Rev **B 42**, 2681, (1990). For a general discussion of the GL functional in the presence of mixed symmetry terms see also R. Joynt, Phys. Rev **B 41**, 4271, (1990); P.I. Soininen, C. Kallin and J. Berlinsky, Phys. Rev **B 50**, 13883, (1994); J. Xu, Y. Ren and C.S. Ting, Phys. Rev **B 53**, R2991, (1996); H. Won and K. Maki, Phys. Rev **B 53**, 5927, (1996).
[20] In writing Eq.(6) one can neglect gradient terms of the type $|D_x(y)\Delta_1|^2$. Near T_c they are proportional to the ratio of the superconducting coherence length at $T = 0$ ξ to the GL coherence length $\xi_{GL} \propto (T_c - T)^{-1/2}$: $(\xi_0/\xi_{GL})^2 (T_c - T)$, whereas the homogeneous quadratic term has no such smallness $\alpha_1 \sim N_0$.
[21] I. A. Lukyanchuk and M. E. Zhitomirsky Supercond. Review 1, 207-257 (1995); cond-mat/9501091
[22] V.P. Mineev and K. Samokhin, "Introduction in the theory of unconventional superconductors", MPTE, Moscow 1998.
[23] L. D. Landau and E. M. Lifshitz, "Quantum Mechanics", see chapter 12, p.378, Pergamon Press, 3-d edition, 1977.
[24] See for example Z. Tezanovich, Physica C **220**, 303, (1994) and referencies therein.